



Wood Flooring Made From Forest Restoration Material

Throughout the West, our National Forests face an increased risk of catastrophic wildfire because of an overabundance of dense, overstocked forest stands. To restore our forests to a healthy state, stands need thinning.


The USDA Forest Service and U.S. Department of Interior have targeted more than \$30 billion over the next decade to reduce hazardous fuels, restore damaged ecosystems, and help communities better protect themselves from catastrophic forest fires. A big part of this effort includes working with communities, entrepreneurs, researchers, and others to search for profitable uses for logs with diameters as small as 4 inches.

There are many potential uses for small-diameter and low-valued forest thinnings. The key is finding the right use within the economics of the location, manufacturing process, and potential markets.

Prime Market

One company who has developed a high-valued, economic use for forest thinnings is North Slope Sustainable Wood, LLC, located in Missoula, Montana.

North Slope offers random length tongue and groove flooring made from small-diameter western larch logs that are harvested from forest restoration projects throughout the Northern Rocky Mountains.

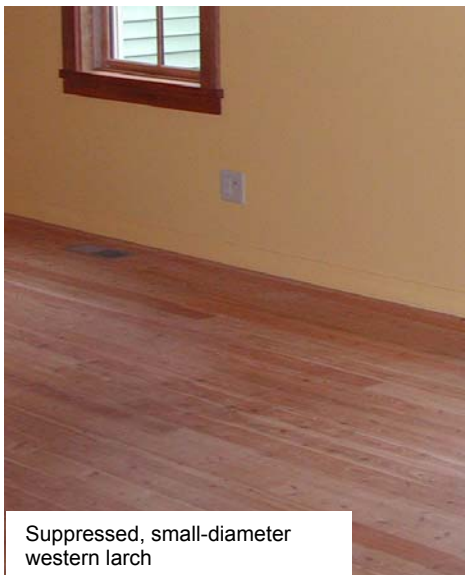

Suppressed, small-diameter western larch

Western larch thrives in the Missoula area. The tree is also known as Montana larch and western tamarack.

Wood flooring constitutes a prime market for millions of board feet of lumber cut from high-quality hardwood and softwood species.

The popularity of wood flooring has continued for centuries. The extensive and prolonged use of wood for flooring indicates that it possesses the special properties, qualities, and characteristics that are particularly desirable for this use, such as

- Distinctive and attractive appearance, with wide latitude for adaptability to the style and motif of the home
- Good hardness and wearing qualities, yet with a degree of resilience that provides comfort
- Low heat conductivity, which assures a feeling of warmth to the touch
- Simplicity and facility of installation
- Relative freedom from slipperiness, depending upon the finish used

Hardwoods Versus Softwoods

Although hardwood species are generally more popular as a flooring material, higher density softwood species are also used. Softwood species that are regularly manufactured into flooring include southern pine, Douglas-fir, western hemlock, and western larch. Hardness and shrinkage values for these species are summarized in Table 1. Hardness values of these softwoods are 33% to 53% less than those of red oak, and 12% to 35% more stable (red oak is a standard hardwood comparison used by the flooring industry).



Suppressed, small-diameter Douglas-fir

| Table 1- Hardness and shrinkage values | | | | |
|---|--------------------------|------------------------------|----------------------------|----------------------|
| Softwoods | Property | | Relative to Red Oak | |
| | Hardness (pounds) | Shrinkage Coefficient | Hardness (%) | Stability (%) |
| Species Average | | | | |
| Douglas-fir | | | | |
| Coast | 710 | 0.00267 | -45 | +28 |
| Interior north | 600 | 0.00241 | -53 | +35 |
| Western Larch | 830 | 0.00323 | -36 | +12 |
| Southern pine | | | | |
| Shortleaf | 690 | 0.00271 | -47 | +27 |
| Longleaf | 870 | 0.00263 | -33 | +29 |
| Western Hemlock | 540 | 0.00274 | -35 | +26 |
| Northern red oak (ref.) | 1290 | 0.00369 | -- | -- |
| Suppressed, Small-Diameter Trees | | | | |
| Douglas-fir | 864 | -- | -- | -- |
| Western larch | 886 | -- | -- | -- |

Small-Diameter Versus Large Diameter

Some literature erroneously suggests that wood cut from small-diameter trees is weaker than wood cut from large-diameter trees. USDA Forest Service research has established that the properties of wood from small-diameter trees may be just as good as those cut from large-diameter trees. Because flooring is a high value product that can be produced from small-diameter softwood trees, there is considerable interest in how the properties of such material compares with those traditionally assumed for western softwood species.

The physical and mechanical properties of small-diameter trees thinned from overstocked stands are dependent upon species, the age of the tree, and the conditions under which the tree is growing. As part of a Forest Service evaluation of utilization options for wood salvaged from forest thinnings, the Forest Products Laboratory evaluated the hardness of two species currently being used in the West for finish flooring—Douglas-fir and western larch.

Several Douglas-fir 2x4s were obtained from suppressed growth trees in northern California and a limited amount of western larch flooring was provided by North Slope Sustainable Wood, LLC. The larch flooring was cut from suppressed, small-diameter trees growing in Montana.

Janka hardness tests were conducted on 120 Douglas-fir 2x4s and 23 pieces of western larch flooring that

had been conditioned to a moisture content of 12%. The results indicate that the suppressed Douglas-fir was 22% to 44% greater than species average hardness values commonly assumed for Douglas-fir. The western larch results were about 6% greater than commonly assumed for larch. It should be cautioned that these property values may not be typical of small-diameter trees of a young age or trees growing in more open stands (e.g., plantations). This caution is especially important for shade-intolerant trees such as larch and ponderosa pine.

For Additional Information Contact

USFA Forest Service
S&PF Technology Marketing Unit
Madison, WI 53705-2398
608-231-9504
<http://www.fpl.fs.fed.us/tmu>

National Wood Flooring Association
111 Chesterfield Industrial Boulevard
Chesterfield, Missouri 63005
1-800-422-4556
www.woodfloors.org

North Slope Sustainable Wood, LLC
P.O. Box 8846
Missoula, MT 59807
406-327-1123 (Mike Wood)
northslopedwood@montana.com